

Structure and stability of the Si(331)-(12×1) surface reconstruction

Corsin Battaglia and Philipp Aebi

*Institut de Physique, Université de Neuchâtel, 2000 Neuchâtel, Switzerland**

Katalin Gaál-Nagy and Giovanni Onida

Dipartimento di Fisica and European Theoretical Spectroscopy Facility (ETSF), Università di Milano, 20133 Milano, Italy

(Dated: February 5, 2009)

We recently proposed a new structural model for the Si(331)-(12×1) surface reconstruction containing silicon pentamers as elementary structural building blocks. Using first-principles density-functional theory we here investigate the stability of a variety of adatom configurations and determine the lowest energy configuration. We also present a detailed comparison of the energetics between our model for Si(331)-(12×1) and the adatom-tetramer-interstitial model for Si(110)-(16×2), which shares the same structural building blocks.

I. INTRODUCTION

High-index silicon surfaces are of interest not only from a fundamental point of view, but also as potential substrates for electronic device fabrication. The reconstructed Si(331)-(12×1) surface is of particular importance since it is the only confirmed planar silicon surface with a stable reconstruction located between the (111) and (110) directions. Due to its large unit cell and its pronounced structural anisotropy it represents a promising template for the growth of low-dimensional heteroepitaxial nanostructures such as quantum dots and nanowires.¹

Since its discovery more than 17 years ago² several structural models containing dimers and adatoms as elementary structural building blocks have been proposed.^{3,4} We recently revealed the presence of an additional building block on the Si(331)-(12×1) surface.⁵ Using scanning tunneling microscopy (STM) we were able to resolve for the first time rows of pentagon pairs running across the Si(331) surface. Very similar pentagons were observed earlier on the reconstructed Si(110) and Ge(110) surfaces.^{6,7,8} Inspired by structural elements encountered on Si(113) and Ge(113) surfaces,^{9,10,11} An *et al.*⁶ have proposed an adatom-tetramer-interstitial (ATI) model for the Si(110)-(16×2) reconstruction containing silicon pentamers as building blocks which explain the pentagons observed in STM images. The stability of the ATI model has subsequently been tested theoretically by means of first-principles total energy calculations.^{12,13} Based on a detailed analysis of our experimental results and a comparison between the Si(110) and Si(331) surface, we proposed a new structural model for the Si(331)-(12×1) reconstruction containing silicon pentamers as essential building blocks.⁵

In order to account for the pentagons observed in our STM images, the model contains two pentamers per (12×1) unit cell, which saturate a certain number of energetically unfavorable dangling bonds of the bulk-truncated Si(331) surface. Some of the remaining dangling bonds are saturated by simple adatoms. The

pentamer positions and bonding configurations were determined exclusively using experimental information and by comparing Si(331) to Si(110) as discussed in detail in Ref. 5. Although the available body of experimental results allows to narrow down the location of the adatoms, currently we do not have sufficient evidence to precisely determine the adatom positions on the surface solely based on information derived from experiment. In this paper we use first-principles total energy calculations to determine the precise adatom positions by finding the lowest energy configuration among various alternative adatom configurations.

The paper is organized as follows: After briefly reviewing the methods used for the calculations, we focus on the bulk-truncated Si(331) surface and compare its energetics to other silicon surfaces, which are known to be stabilized by surface reconstructions. In a second step pentamers are introduced and the consequences on the total energy are discussed. Then we consider a variety of candidate adatom configurations and determine the one with the lowest energy. At the end we discuss the impact of the remaining dangling bonds on the total energy.

II. THEORY

A. Computational details

Our results are based on first-principles calculations within density-functional theory (DFT),^{16,17} using the local-density approximation (LDA) for the exchange-correlation functional.^{18,19} We adopt a plane-wave basis set and norm-conserving pseudopotentials, as implemented in the PWSCF code of the QUANTUM-ESPRESSO suite.²⁰ Pseudopotentials for silicon and hydrogen are chosen in the von Barth style.^{21,22}

The Si(331) surface was simulated by means of an atomic slab and a repeated supercell, in order to recover a three-dimensional periodicity. The slab thickness corresponds to 10 silicon double layers (DLs), and the periodic images are separated by 9.4 Å of vacuum. Since each bulk DL

TABLE I: Surface energies for unrelaxed bulk-truncated surfaces of various orientations. The numbers in parenthesis give the number of surface atoms and dangling bonds per (1×1) unit cell respectively.

Surface orientation	Surface atom density ($\text{\AA}^{-2}$)	Dangling bond density ($\text{\AA}^{-2}$)	Estimated surface energy (meV/ $\text{\AA}^2$)	Calculated surface energy (meV/ $\text{\AA}^2$)
(111)	0.078 (1)	0.078 (1)	90.1	113.6 ¹⁴
(100)	0.068 (1)	0.136 (2)	155.9	149.2 ¹⁴
(113)	0.082 (2)	0.123 (3)	141.0	137.9 ¹⁵
(110)	0.096 (2)	0.096 (2)	110.3	127.3 ¹⁴
(331)	0.093 (3)	0.093 (3)	107.3	127.2 ^a

^athis work

contains 24 silicon atoms, our supercell counts 240 silicon atoms plus a number of silicon atoms at the top surface (varying from 0 to 14 depending on the specific reconstruction). The bottom surface of the slab is hydrogen-passivated (with 36 hydrogen atoms).

Since we are interested in small energy differences, we adopt strict convergence criteria with respect to both the kinetic-energy cutoff and the sampling of the surface Brillouin zone. In particular, the inclusion of plane waves up to 544 eV (40 Ry) and the use of a xy shifted $3\times 4\times 1$ Monkhorst-Pack grid²³ for the $\mathbf{k}$ point sampling allowed us to ideally compute total energy differences with an accuracy of the order of 15 meV/supercell. By taking into account the fact that our relaxed structures still show small residual forces (see below), we estimate our numerical accuracy on calculated surface energies to be better than 0.1 meV/ $\text{\AA}^2$. All structures were optimized till the largest residual force on the mobile atoms was less than 0.026 eV/ $\text{\AA}$ (0.001 Ry/Bohr).

The hydrogen atom positions were determined in a first run by optimizing them on a bulk-terminated slab with fixed bulk-like positions for silicon atoms, with top and bottom surfaces saturated by hydrogen. In all the following calculations we have taken hydrogen atomic positions at the bottom surface as fixed. In a second step, we inspected the decay of forces in the direction perpendicular to the surface, for a slab containing a non-relaxed surface reconstruction. A nearly force-free bulk region is reached after the five topmost DLs. Thus, only the topmost five bulk silicon DL were allowed to relax together with the surface (reconstruction) atoms, where the inner DLs have been kept fixed. All results presented below are based on a slab relaxed in this way.

B. Determination of the surface energy

The surface energy E_{surf} of a double-sided symmetric slab containing N_{Si} silicon atoms can be written as¹⁴

$$E_{\text{surf}} = \frac{1}{2}(E_{\text{tot}}(N_{\text{Si}}) - \mu_{\text{Si}}N_{\text{Si}}) \quad , \quad (1)$$

where μ_{Si} is the chemical potential of silicon, being simply the bulk energy per atom at zero temperature. This

value can be obtained from a simple bulk silicon calculation. $E_{\text{tot}}(N_{\text{Si}})$ is the total energy of the slab. The factor of 2 comes from the fact that there are two identical surfaces. For a non-symmetric slab for which only the bottom surface is saturated by hydrogen atoms, we have

$$E_{\text{surf}} + E_{\text{surf}}^{\text{H}} = E_{\text{tot}}(N_{\text{Si}}, N_{\text{H}}) - \mu_{\text{Si}}N_{\text{Si}} - \mu_{\text{H}}N_{\text{H}} \quad (2)$$

Here, $E_{\text{surf}}^{\text{H}}$ is the surface energy of the hydrogen saturated surface, μ_{H} is the chemical potential for the hydrogen atoms, and $E_{\text{tot}}(N_{\text{Si}}, N_{\text{H}})$ is the total energy of the slab whose bottom surface is saturated by N_{H} hydrogen atoms. Therefore, we have

$$E_{\text{surf}} = E_{\text{tot}}(N_{\text{Si}}, N_{\text{H}}) - \mu_{\text{Si}}N_{\text{Si}} - \mu_{\text{H}}N_{\text{H}} - E_{\text{surf}}^{\text{H}} \quad . \quad (3)$$

In order to avoid the determination of μ_{H} , we consider the following: The total energy of the slab can be written as

$$E_{\text{tot}}(N_{\text{Si}}, N_{\text{H}}) = \frac{1}{2}E_{\text{tot}}^{\text{H}} + \frac{1}{2}E_{\text{tot}} \quad (4)$$

where $E_{\text{tot}}^{\text{H}}$ is the total energy of a symmetric hydrogen saturated slab and E_{tot} is the total energy of a symmetric slab containing the surface reconstruction. The value $E_{\text{tot}}^{\text{H}}$ has been calculated in the preliminary run used for the determination of the hydrogen positions. The surface energy (per unit area) for the top surface carrying the surface reconstruction can then be determined using

$$\gamma = E_{\text{surf}}/A = (E_{\text{tot}}(N_{\text{Si}}, N_{\text{H}}) - \frac{1}{2}E_{\text{tot}}^{\text{H}} - \tilde{N}_{\text{Si}}\mu_{\text{Si}})/A \quad (5)$$

where $\tilde{N}_{\text{Si}}$ is the number of silicon atoms in the upper half slab and A the surface area of the slab.

III. RESULTS AND DISCUSSION

A. Bulk-truncated surface

In order to define an energy reference for the following discussion we have determined the surface energy for the unrelaxed bulk-truncated Si(331) surface shown in Fig. 1(a) and (b). The value of 127.2 meV/ $\text{\AA}^2$ may be

compared in Tab. I with the values for other surface orientations.

The surface energy of a bulk-truncated surface can be estimated from the cohesive energy of silicon, which is $E_c = 4.6$ eV per atom.²⁴ The cohesive energy of a solid is the energy per atom required to break the atoms of the solid into isolated atomic species. Since a bond is formed by two atoms and each silicon atom makes four bonds, the energy required to break a bond is half the cohesive energy, i.e. $E_b = 2.3$ eV per bond.²⁵ The surface energy γ can now be estimated by multiplying the bond energy E_b by the density of broken bonds n .²⁶ The latter is the number of dangling bonds N per surface area A , $n = N/A$. Thus $\gamma = NE_b/2A = nE_b/2$. The factor of 2 takes into account that two surfaces are created.

Note that the dangling bond density n is not necessarily equal to the surface atom density (see values in paren-

thesis in Tab. I). This is due to the fact that a surface atom may either carry one or two dangling bonds. (111)-like surface atoms carry a single dangling bond, whereas (100)-like surface atoms carry two dangling bonds (see Fig. 3(a) and 2(a) respectively in Ref. 27). On the (113) surface, both types of surface atoms coexists, whereas on the (110) and the (331) surface only (111)-type surface atoms occur (see Fig. 5(a), 6(a) and 7(a) respectively in Ref. 27).

In Tab. I we summarize estimated and calculated surface energies of unrelaxed bulk-truncated surfaces for a series of surface orientations. Although the simple estimate based on the cohesive energy fails to precisely reproduce the values determined with the help of first-principles methods, it correctly reproduces the energy ordering of the various surfaces. The estimated values tend to underestimate the surface energy for surfaces containing only (111)-type surface atoms, whereas they overestimate the surface energy for surfaces with (100)-type surface atoms. For Si(113), which contains both types of surface atoms, these two tendencies compensate resulting in the best agreement between estimated and calculated value.

From the theoretical point of view, the most stable surface is the one with the lowest surface energy. Consequently only structural models for the reconstructed surface with a surface energy lower than the bulk-truncated surface must be considered. Allowing the bulk-truncated surface to relax and determining the corresponding surface energy, we obtain an even more stringent condition on the surface energy for any valid candidate model. The relaxed structure of the bulk-truncated Si(331) surface is shown in Fig. 2(a). Note that although the relaxation was performed within the (12×1) supercell, it did not break the (1×1) periodicity within our numerical accuracy. The surface energy for the relaxed bulk-truncated surface is given in Tab. II along with the surface energies for other structures for the Si(331) and Si(110) surface discussed hereafter. Relaxation of the bulk-truncated Si(331) surface within the (12×1) unit cell results in a reduction of the surface energy of $16.3 \text{ meV}/\text{\AA}^2$, a value to be compared with the corresponding value of $21.2 \text{ meV}/\text{\AA}^2$ for Si(110) obtained by Stekolnikov *et al.*¹³ via relaxation of the bulk-truncated Si(110) surface within the (16×2) cell.

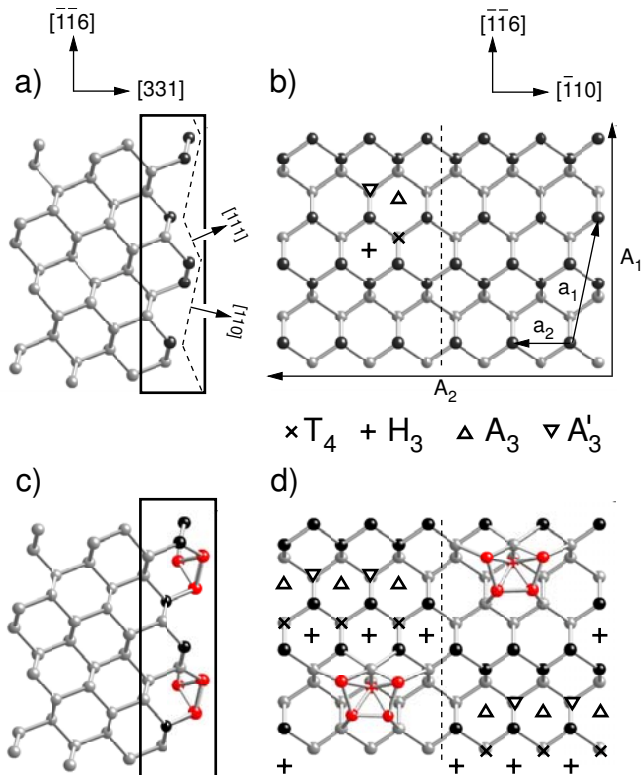


FIG. 1: (Color online) Side (a)/(c) and top view (b)/(d) of the unrelaxed bulk-truncated Si(331)- (12×1) surface unit cell/unrelaxed 'pentamers only' model. The bulk directions are given. In (b)/(d) only the topmost atoms contained within the rectangle in (a)/(c) are shown. Subsurface atoms are shown in grey, undercoordinated surface atoms in black, pentamer atoms in red. In (a) the Si(111) and Si(110) terraces composing the Si(331) surface are indicated. In (b) the (1×1) and (12×1) surface unit cell vectors $\mathbf{a}_1$, $\mathbf{a}_2$ and $\mathbf{A}_1$, $\mathbf{A}_2$ respectively are also drawn. The orientation of the glide plane is indicated by a dashed line. In (b) the four different types of adatom adsorption sites T_4 , H_3 , A_3 and A'_3 are represented by markers. In (d) the 2×12 possible adatom positions after introduction of the two pentamers are shown.

B. Pentamers

The bulk-truncated Si(331) surface consists of alternating single and double rows of undercoordinated surface atoms running along the $[\bar{1}10]$ direction (black atoms in Fig. 1(a) and (b)). Each of the 36 (111)-type surface atoms per (12×1) unit cell carries one dangling bond, which renders the unreconstructed structure energetically unfavorable.

In our model, 10 out of the 36 dangling bonds are saturated by two silicon pentamers observed as pentagons in STM images. Their integration onto the bulk-truncated

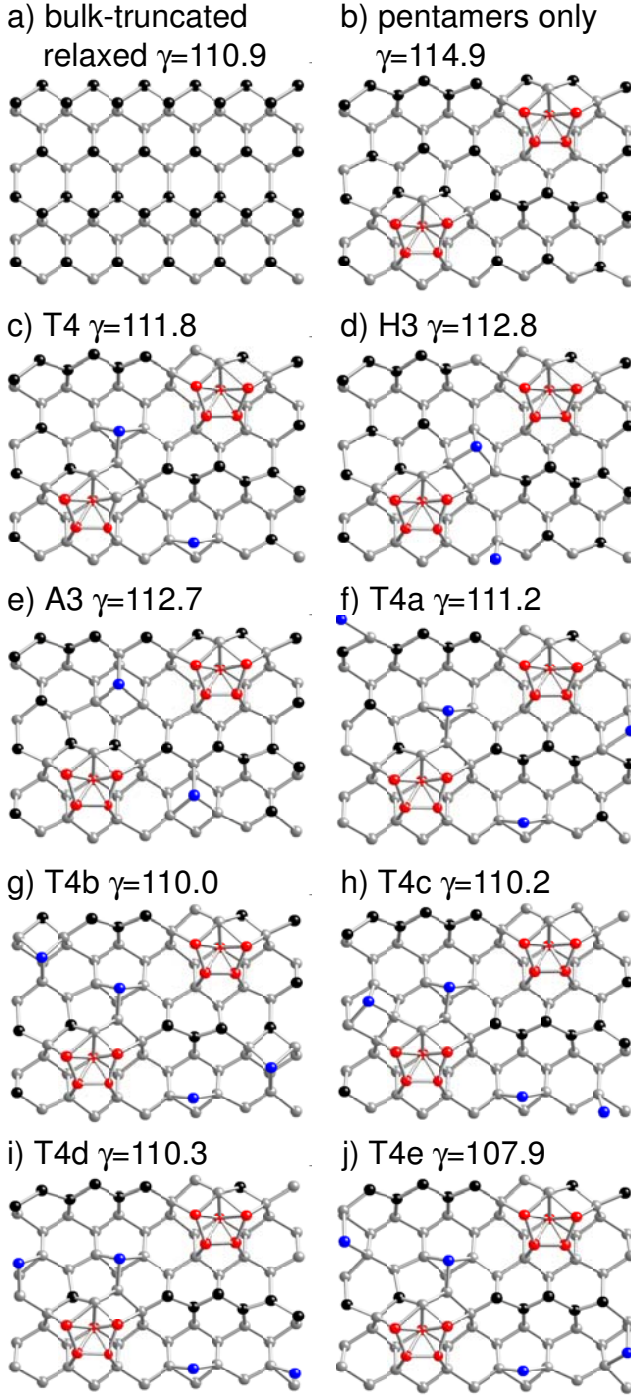


FIG. 2: (Color online) (a) Top view of the relaxed bulk-truncated Si(331)-(12 $\times$ 1) surface. (b) Top view of the relaxed 'pentamers only' model. (c)-(j) Various candidate adatom configurations of the adatom-pentamer model. The surface energy γ for each model is given in units of meV/ $\text{\AA}^2$.

Si(331) surface was discussed in detail in Ref. 5. It is important to note that the bulk-truncated Si(331) surface may be viewed as a highly stepped surface consisting of small alternating Si(111) and Si(110) terraces (see

TABLE II: Comparison between the surface energies of various surface structures of Si(331) and Si(110)

Structure	Surface energy (meV/ $\text{\AA}^2$)	
	Si(331)	Si(110)
bulk-truncated	127.2 ^a	127.3 ¹⁴
bulk-truncated relaxed	110.9 ^a	106.1 ^{13,14}
pentamers only	114.9 ^a	108.6 ^{13,14}
adatoms and pentamers	107.9 ^a	103.8 ^{13,14}

^athis work

Fig. 1(a)). This allows to anchor the pentamers on the Si(331) surface in exactly the same local binding configuration as on the Si(110) surface, where pentamers are also observed. Introducing two pentamers per unit cell as shown in Fig. 1(c) and (d) reduces the number of dangling bonds from 36 to 26 and lowers the surface energy (for the corresponding relaxed model shown in Fig. 2(b)) by 12.3 meV/ $\text{\AA}^2$ with respect to the unrelaxed bulk-truncated surface (see Tab. II). This value is comparable with the reduction of 18.7 meV/ $\text{\AA}^2$ obtained when introducing four pentamers onto the Si(110)-(16 $\times$ 2) surface (corresponding to the tetramer-interstitial (TI) model in Ref. 13, note that in the TI model the step is already included into the unit cell accounting for 1.0 meV/ $\text{\AA}^2$ energy reduction). However, the 'pentamers only' models for both, Si(331) and Si(110), are not stable structures, since the relaxed bulk-truncated surface for both surfaces possesses a lower surface energy. This is not surprising, since the introduction of pentamers suggested by STM images, leaves a lot of dangling bonds unsaturated. So an additional building block is required to stabilize the structures containing pentamers.

C. Adatoms

In the ATI model for Si(110)-(16 $\times$ 2), the pentamer structure is stabilized by adatoms. Among the various elementary structural building blocks observed in silicon surface reconstructions (see Ref. 27 for a review), adatoms impose themselves also as the best choice for Si(331) to saturate some of the remaining 26 dangling bonds for the following two reasons: Firstly, as mentioned before, the bulk-truncated Si(331) surface may be viewed as being composed of small alternating (110) and (111) terraces. Since adatoms are observed on both the Si(110) and the Si(111) surface, the Si(331) consequently provides exactly the same local environment for adatoms as on Si(110) and Si(111). Secondly adatoms allow to explain the additional protrusions seen in STM images, which can not be attributed to the pentamer atoms.⁵ An adatom requires three unsaturated surface atoms to be attached to. On the (111) terraces of the Si(331) surface, adatoms may occupy two possible sites indicated in Fig. 1(b). These geometries are distinguished as hollow (H_3) and atop (T_4) sites depending on whether the sub-

strate atoms below the adatom is found in the fourth or second layer. In H_3 sites the adatom is three-fold coordinated, in T_4 sites the adatom is approximately four-fold coordinated due to the substrate atom directly below in the second layer.

On the (110) terraces of the Si(331) surface, we can also distinguish between two different three-fold coordinated adsorption sites depending on their orientation labeled A_3 and A'_3 in Fig. 1(b). Note that on the bulk-truncated (110) surface these two sites become equivalent due to the mirror symmetry of the (110) surface along the $[\bar{1}10]$ direction (not shown).

Careful inspection of Fig. 1(d) shows that after introducing two pentamers per unit cell there are exactly 2×12 possible positions for placing adatoms, the factor of 2 is due to the glide plane symmetry along the $[\bar{1}1\bar{6}]$ direction (dashed line in Fig. 1(d)). Out of the 2×12 candidate adsorption sites, we identify 2×3 T_4 sites, 2×4 H_3 sites, 2×3 A_3 sites and 2×2 A'_3 sites. This however does not imply that a maximum of 24 adatoms can be placed on the surface. The reason for this is as follows. After placing a first adatom on the surface, some surrounding candidate sites can not be occupied by an adatom anymore, since they shared the same dangling bond with the now occupied site, whose adatom saturates this dangling bond.

A first pair of adatoms must be placed between two successive pentamers, in order to account for the clear protrusions seen in STM images.⁵ Due to the glide plane symmetry adatoms must always occur in pairs. There are only three candidate sites for this first adatom: a T_4 site (Fig. 2(c)), a H_3 site (Fig. 2(d)) and a A_3 site (Fig. 2(e)). Using first-principles calculations we have tested these three possible adatom configurations and found that the T_4 site is the most stable of the three (surface energies for each model are also given in Fig. 2). This is not surprising, since T_4 sites are commonly favored over the H_3 sites on (111) surfaces such as in the Si(111)-(7×7) reconstruction and the Ge(111)-c(2×8) reconstruction (see Ref. 27 for a review of their structural models). In addition the T_4 adatom position reproduces best the protrusion observed by STM between two successive pentagons.⁵

Consequently, in order to reduce the large number of potential candidate adatom configurations to a computationally manageable number of models, we have restricted our further investigations to the subset of models containing the T_4 adatom pair. In a second step we have investigated *all* possible remaining positions for a second pair of adatoms. There are exactly five candidate configurations to be considered (shown in Fig. 2(f)-(j)). Using first-principles calculations we find that a A_3 adatom position (configuration T4e) gives the most stable configuration. The position of the A_3 adatom pair is also in agreement with light protrusions seen in STM images⁵. After placing this A_3 adatom pair there is no more candidate site left on which one could place an additional adatom.

As discussed before, the introduction of two pentamers

TABLE III: Surface energies for silicon surface reconstructions

Reconstruction	Surface energy (meV/Å ²)
Si(111)-(7×7)	84.9 ¹⁴
Si(100)-c(4×2)	88.0 ¹⁴
Si(113)-(3×2)	87.9 ²⁸ /87.4 ¹⁴
Si(110)-(16×2)	103.8 ^{13,14}
Si(331)-(12×1)	106.4 ^a

^athis work

is not sufficient to obtain a lower surface energy than for the relaxed bulk-truncated surface. Inspection of Tab. II shows that adding adatoms to the pentamers allows to sufficiently lower the surface energy to render the reconstructed surface more stable than the relaxed bulk-truncated surface, for both the Si(331) and the Si(110) surfaces (reduction of surface energy by 7.0 meV/Å² and 4.8 meV/Å² respectively with respect to the 'pentamers only' models).

D. Rest atoms

Introducing two T_4 and two A_3 adatoms per unit cell into our structural model for the Si(331)-(12×1) reconstruction further reduces the number of dangling bonds from 26 to 14 (10 of the 36 dangling bonds are saturated by the pentamers, introducing 4 adatoms further eliminates 4×3 dangling bonds (here we do not count the dangling bond carried by each adatom)). The remaining 14 surface atoms, which still carry a dangling bond, are so called rest atoms (black atoms in Fig. 2(i)). Rest atoms are common structural building blocks accompanying adatoms. The adatom model for the Ge(111)-c(2×8) reconstruction is built from four adatoms and four rest atoms. For this case, we have an ideal one-to-one correspondence between adatoms and rest atoms. Each adatom delivers one electron from its dangling bond to fill the dangling bond of the rest atom resulting in a further decrease of the surface energy. In contrast, in the famous dimer-adatom-stacking fault (DAS) model of the Si(111)-(7×7) reconstruction, there are 12 adatoms, but only 6 rest atoms plus the corner hole atom, which behaves similarly to a rest atom. In this case, using a simple ionic picture, we have 7 electrons which are transferred from the adatoms into the rest atom plus corner hole atom states, but five electrons remain in the adatoms bands. For the ATI model of the Si(110)-(16×2) reconstruction, there are 8 adatoms and 12 rest atoms. So even when transferring the 8 electrons from the adatoms to the rest atoms, only a fraction of the rest atoms may saturate their dangling bonds. Similarly in our model, with four adatoms and 14 rest atoms, we expect some remaining unsaturated rest atoms.

The unequal adatom:rest atom ratio between the ATI model (8:12=0.67) of Si(110) and our model (4:14=0.29) of Si(331) might on the first view explain why the ATI model exhibits a slightly lower surface energy than our model (energy difference 4.1 meV/Å², see Tab. II). Reinspection of Tab. II however reveals that this energy difference between Si(331) and Si(110), whose corresponding unrelaxed bulk-truncated surfaces have almost the same energy (energy difference only 0.1 meV/Å²), is already present for the respective 'pentamers only' models (energy difference between 'pentamers only' models 6.3 meV/Å²). It is also interesting to note that the introduction of the adatoms leads to a larger reduction of the surface energy for Si(331) (7.0 meV/Å²) than for Si(110) (4.8 meV/Å²) with respect to the 'pentamers only' models.

Introducing hypothetically an additional adatom pair into our model for Si(331) would improve its adatom:rest atom ratio from 4:14=0.29 to 6:8=0.75. The introduction of the first pair of adatoms (T_4) accounts for a reduction of 3.1 meV/Å² of the surface energy. Adding a second pair of adatoms (A_3) to the first pair allowed to reduce the surface energy by 3.9 meV/Å². Following this tendency, by assuming an energy gain of 3-4 meV/Å² for the introduction of a hypothetical third pair of adatoms into our model, suggests that the surface energy of Si(331) comes to lie close to the value determined for Si(110) by Stekolnikov *et al.*¹³. However, note that the rest atom geometry of T4e does not allow the introduction of an additional adatom pair. When considering the subset of T4x models (with x=a-e), only configurations T4a and T4b admit a pair of free adatom sites, resulting in configuration T4a+b. But this configuration was discarded because it is not compatible with the experimental STM images.⁵

Several more three adatom pair configurations are possible when studying H3x (8/7 possible two/three adatom pair configurations) or A3x configurations (5/1 possible two/three adatom pair configurations). Even more possibilities may exist when allowing the placement of the first adatom pair on a different site. Here we focused on the family of T4x models, whose selection was motivated and justified in section C. Before testing other potential configurations, further experimental hints on the position of the adatoms from complementary experimental techniques are necessary to assist in the search for the lowest energy configuration.

When compared to the surface energies of reconstructions on surfaces with other orientations listed in Tab. III, the models for the Si(110)-(16×2) and the Si(331)-(12×1) reconstruction have surface energies which are of the order of 20 meV/Å² higher than the surface energies for Si(111)-(7×7), Si(100)-c(4×2) and Si(113)-(3×2). As it was already mentioned by

Stekolnikov *et al.*¹³ in the context of the ATI model for Si(110)-(16×2), a completely new, more complex reconstruction model cannot be excluded. Nevertheless, the advantage of our method for developing a structural model for Si(331)-(12×1) consists here in integrating elementary structural building blocks such as pentamers and adatoms identified on the (110) and (111) silicon surfaces²⁷ onto the bulk-truncated Si(331) surface. The consistency of the pentamer building block with all currently available experimental data on Si(331)-(12×1), but also on Si(110)-(16×2), represents further indirect evidence in favor of the two structural models. It should be noted, that our model for Si(331) is far from a simple extension of the Si(110) surface to its vicinals. The pentagons on Si(110) (see Fig. 6 in Ref. 27) are arranged in pairs pointing in opposite directions, whereas on Si(331) pairs point in the same direction. Also the direction of the double pentagon rows appears to be completely unrelated between the two surfaces. Using pentamers and adatoms we succeeded in combining these seemingly conflicting experimental observations in a coherent picture.

IV. SUMMARY AND CONCLUSIONS

Using first-principles density-functional theory we studied the stability of the structural model for the Si(331)-(12×1) surface reconstruction, which we recently proposed. In particular we determined the energetically most favorable adatom configuration among a variety of candidate structures. We find that a configuration with a pair of T_4 adatoms and a second pair of A_3 adatoms results in the lowest energy. We also discussed the implications of the rest atoms on the energy and compared our model to other silicon surface reconstructions.

Acknowledgments

Stimulating discussions with Claude Monney, Clément Didiot, Eike Schwier, Nicolas Mariotti, and Michael Gunnar Garnier are gratefully acknowledged. Skillfull technical assistance was provided by our workshop and electric engineering team. This work was supported by the Fonds National Suisse pour la Recherche Scientifique through Div. II and the Swiss National Center of Competence in Research MaNEP. We acknowledge support by the European Community through the "Nanoquanta NoE" and "ETSF-I3" projects (NMP4-CT-2004-500198 and Grant Agreement n. 211956) for the theoretical results, which are an outcome of the ETSF User Project n. 94.

* Electronic address: corsin.battaglia@unine.ch;
URL: <http://www.unine.ch/phys/spectro>

¹ C. Battaglia, C. Monney, C. Didiot, E. F. Schwier, M. Mar-

- iotti, M. G. Garnier, and P. Aebi, arxiv:0809.4967, submitted to AIP Conference Proceedings.
- ² J. Wei, E. D. Williams, and R. L. Park, *Surf. Sci. Lett.* **250**, L368 (1991).
 - ³ B. Z. Olshanetsky, S. A. Teys, and I. G. Kozhemyako, *Phys. Low-Dim. Struct.* **11/12**, 85 (1998).
 - ⁴ Z. Gai, R. G. Zhao, T. Sakurai, and W. S. Yang, *Phys. Rev. B* **63**, 085301 (2001).
 - ⁵ C. Battaglia, K. Gaál-Nagy, C. Monney, C. Didiot, E. F. Schwier, M. G. Garnier, G. Onida, and P. Aebi, arxiv:0807.3875, accepted for publication in *Phys. Rev. Lett.*
 - ⁶ T. An, M. Yoshimura, I. Ono, and K. Ueda, *Phys. Rev. B* **61**, 3006 (2000).
 - ⁷ T. Ichikawa, T. Sueyosi, T. Saot, M. Iwatsuki, F. Udagwa, and I. Sumita, *Sol. Stat. Comm.* **93**, 541 (1995).
 - ⁸ Z. Gai, R. G. Zhao, and W. S. Yang, *Phys. Rev. B* **57**, R6795 (1998).
 - ⁹ J. Dabrowski, H.-J. Müssig, and G. Wolff, *Phys. Rev. Lett.* **73**, 1660 (1994).
 - ¹⁰ A. Laracuenta, S. C. Erwin, and L. J. Whitman, *Phys. Rev. Lett.* **81**, 5177 (1998).
 - ¹¹ A. A. Stekolnikov, J. Furthmüller, and F. Bechstedt, *Phys. Rev. B* **67**, 195332 (2003).
 - ¹² A. A. Stekolnikov, J. Furthmüller, and F. Bechstedt, *Phys. Rev. B* **70**, 045305 (2004).
 - ¹³ A. A. Stekolnikov, J. Furthmüller, and F. Bechstedt, *Phys. Rev. Lett.* **93**, 136104 (2004).
 - ¹⁴ A. A. Stekolnikov, J. Furthmüller, and F. Bechstedt, *Phys. Rev. B* **65**, 115318 (2002).
 - ¹⁵ A. A. Stekolnikov, J. Furthmüller, and F. Bechstedt, *Phys. Rev. B* **68**, 205306 (2003).
 - ¹⁶ P. Hohenberg and W. Kohn, *Phys. Rev.* **136 B**, 864 (1964).
 - ¹⁷ W. Kohn and L. J. Sham, *Phys. Rev.* **140 A**, 1133 (1965).
 - ¹⁸ J. P. Perdew and A. Zunger, *Phys. Rev. B* **23**, 5048 (1981).
 - ¹⁹ D. M. Ceperley and B. J. Alder, *Phys. Rev. Lett.* **45**, 566 (1980).
 - ²⁰ <http://www.pwscf.org>.
 - ²¹ U. von Barth and R. Car (unpublished).
 - ²² A. DalCorso, S. Baroni, R. Resta, and S. de Gironcoli, *Phys. Rev. B* **47**, 3588 (1993).
 - ²³ H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).
 - ²⁴ B. Farid and R. W. Godby, *Phys. Rev. B* **43**, 14248 (1991).
 - ²⁵ W. A. Harrison, *Electronic Structure and Properties of Solids* (Freeman, San Francisco, 1980).
 - ²⁶ J. Dabrowski and H. J. Müssig, *Silicon Surfaces and Formation of Interfaces* (World Scientific, Singapore, 2000).
 - ²⁷ C. Battaglia, K. Gaál-Nagy, C. Monney, C. Didiot, E. F. Schwier, M. G. Garnier, G. Onida, and P. Aebi, *J. Phys.: Condens. Matter* **21**, 013001 (2009).
 - ²⁸ K. Gaál-Nagy and G. Onida, *Phys. Rev. B* **75**, 155331 (2007).